

Electron-phonon coupling and charge gap in spin-density-wave iron-pnictides from quasiparticle relaxation dynamics

L. Stojchevska¹, P. Kusar¹, T. Mertelj¹, V.V. Kabanov¹, X. Lin², G. H. Cao², Z. A. Xu² and D. Mihailovic¹

¹*Complex Matter Dept., Jozef Stefan Institute, Jamova 39, Ljubljana, SI-1000, Ljubljana, Slovenia and*

²*Department of Physics, Zhejiang University, Hangzhou 310027, People's Republic of China*

(Dated: February 12, 2010)

We investigate the quasiparticle relaxation and low-energy electronic structure in undoped SrFe_2As_2 exhibiting spin-density wave (SDW) ordering using optical pump-probe femtosecond spectroscopy. A remarkable critical slowing down of the quasiparticle relaxation dynamics at the SDW transition temperature $T_{\text{SDW}} = 200\text{K}$ is observed. From temperature dependence of the transient reflectivity amplitude we determine the SDW-state charge gap magnitude, $2\Delta_{\text{SDW}}/k_B T_{\text{SDW}} = 7.2 \pm 1$. The second moment of the Eliashberg function, $\lambda \langle (\hbar\omega)^2 \rangle = 110 \pm 10 \text{ meV}^2$, determined from the relaxation time above T_{SDW} , is similar to SmFeAsO and BaFe_2As_2 indicating a rather small electron phonon coupling constant unless the electron-phonon spectral function ($\alpha^2 F(\omega)$) is strongly enhanced in the low-energy phonon region.

The discovery of high-temperature superconductivity in iron-based pnictides [1–3] has attracted a great deal of attention recently. The question of the relative importance of the lattice and spin degrees of freedom for the superconducting pairing interaction becomes immediately apparent, since the superconductivity appears upon doping the parent materials[43] which show the spin-density wave (SDW) ground state. Understanding the parent SDW compounds from the point of electron-phonon and not only the spin-spin and spin-charge interactions is therefore beneficial for understanding the nature of the superconducting coupling in the doped compounds.

Time resolved spectroscopy has been very instrumental in elucidating the nature of the electronic excitations in superconductors, particularly cuprates [4–18] and recently also iron pnictides[19–23]. Moreover, the relaxation kinetics can give us valuable information on the electronic structure[5] and electron-phonon coupling[24].

In this work we present a time-resolved femtosecond spectroscopy study of SrFe_2As_2 in the normal and the SDW state. From the photo-excited carrier relaxation dynamics we determine the electron-phonon coupling parameters and the charge gap magnitude. We compare the results with recent data[23] in SmFeAsO and find that they are similar both in the SDW and normal state with some minor differences in the magnitude of the response at high temperatures.

Optical experiments were performed using the standard pump-probe technique, with 50 fs optical pulses from a 250-kHz $\text{Ti:Al}_2\text{O}_3$ regenerative amplifier seeded with an $\text{Ti:Al}_2\text{O}_3$ oscillator. We used the pump photons with doubled ($\hbar\omega_P = 3.1 \text{ eV}$) photon energy and the probe photons with 1.55 eV photon energy. The pump and probe polarizations were perpendicular to each other and oriented with respect to the crystals to obtain the maximum amplitude of the response at low temperatures. The pump and probe beam diameters were determined by measuring the transmittance of calibrated pinholes mounted at the sample position[25]. Single crystals of

SrFe_2As_2 were prepared by the self-flux method.[26] For optical measurements the cleaved crystals were glued on a Cu plate mounted in an optical liquid-He flow cryostat.

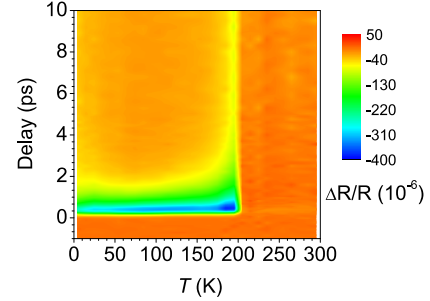


Figure 1: (Color online) $\Delta R/R$ transients as a function of temperature at pump-fluence $17 \mu\text{J}/\text{cm}^2$. A divergent relaxation time at $T_{\text{SDW}} = 200\text{K}$ is clearly seen.

In Fig. 1 we plot the temperature dependence of $\Delta R/R$ transients in SrFe_2As_2 . Below T_{SDW} the transients are dominated by the initial single exponential relaxation followed by a weak structure at around 10 ps (see Fig. 2 (a)). At T_{SDW} a critical slowing down of relaxation is observed in the form of a long lived relaxation which is following the initial $\sim 1 \text{ ps}$ exponential decay. Above T_{SDW} the amplitude of the initial sub-ps relaxation strongly drops and the structure on a longer timescale becomes apparent. The behavior is similar to SDW SmFeAsO [23] with the exception of the sub-ps relaxation amplitude above T_{SDW} being smaller in SrFe_2As_2 .

The amplitude of the initial sub-ps peak shows a minor departure from the linear pump fluence ($\mathcal{F}$) dependence at the highest $\mathcal{F}$ (see Figs 3 and 4) while the sub-ps relaxation time is virtually $\mathcal{F}$ independent (see Fig. 4). At low T however, an additional non-exponential slow relaxation component appears at the lowest fluence (see Fig. 3) which can be (beyond 5-10 ps) attributed to the heat diffusion out of the excitation volume[27] as indicated by

fits in Fig. 3.

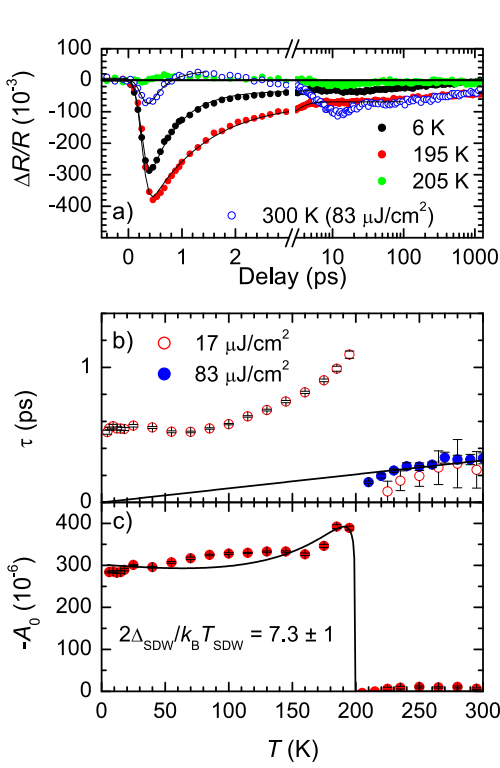


Figure 2: (Color online) $\Delta R/R$ transients at representative temperatures with single-exponential decay fits (a). The relaxation time at two pump fluences (b) and amplitude at $\mathcal{F} = 17 \mu\text{J}/\text{cm}^2$ (c) as functions of temperature. The black solid line in (b) is fit of equation (1) to τ above 230K. The black solid line in (c) represents the fit of equation (6) from [5].

In a metal the photoexcited-quasiparticle relaxation time is governed by transfer of energy from electronic degrees of freedom to the lattice degrees of freedom. Recently the problem was solved analytically[24]. In bad metals, above the Debye frequency (ω_D), the relaxation time linearly depends on the temperature, T , where the slope is determined by the inverse of the second moment of the Eliashberg function $\lambda\langle\omega^2\rangle$:[24, 28]

$$\tau = \frac{2\pi k_B T}{3\hbar\lambda\langle\omega^2\rangle}. \quad (1)$$

We find that above ~ 230 K our τ -data nicely follow the predicted linear T dependence (see Fig. 2 (b)) with $\lambda\langle(\hbar\omega)^2\rangle = 110 \pm 10 \text{ meV}^2$. The phonon spectrum of SrFe_2As_2 extends up to $\sim 40 \text{ meV}$ with the acoustic phonon cutoff at $\sim 10 \text{ meV}$. [29] We determine $\lambda\langle(\hbar\omega)^2\rangle/\lambda$ by assuming that the electron-phonon spectral function,

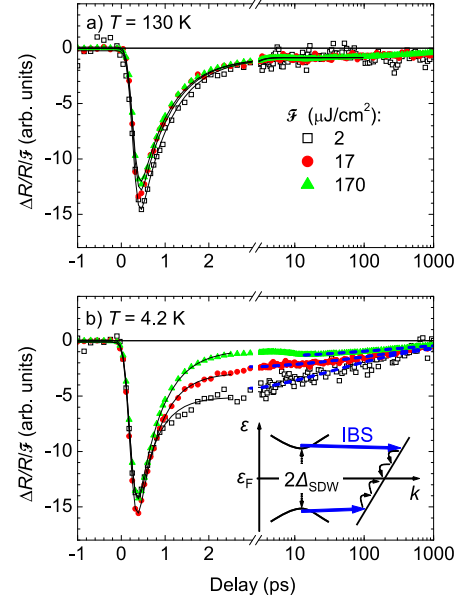


Figure 3: (Color online) Fluence dependence of normalized $\Delta R/R$ transients in the SDW state. The black thin lines are single exponential decay fits and blue dashed lines the 1D diffusion[27] fits. In the inset to (b) the relaxation pathway via inter-band scattering, that is discussed in text, is schematically shown.

$\alpha^2 F(\omega)$, has the phonon DOS shape[29, 30] and obtain $\lambda\langle(\hbar\omega)^2\rangle/\lambda \simeq 430 \text{ meV}^2$. This gives $\lambda \simeq 0.25$, which is rather low to explain the superconducting critical temperatures in doped compounds within a standard single band BCS model.[30] If however, $\alpha^2 F(\omega)$ is for some reason enhanced in the low-energy phonons region, λ could easily reach significantly higher values.

Below T_{SDW} the increasing amplitude of the subps transients indicates the appearance of a bottleneck in the photo-excited electron relaxation. The bottleneck is associated with opening of a T -dependent gap[5] due to SDW formation resulting in the Fermi surface reconstruction[31, 32]. We use equation (6) from Kabanov *et al.*[5], which describes the photo-excited change in quasiparticle density in the presence of a temperature dependent gap, to fit the amplitude below $T_{\text{SDW}} = 200$ K. Using a single SDW gap energy with the BCS temperature dependence and $2\Delta_{\text{SDW}}/k_B T_{\text{SDW}} \simeq 7.2 \pm 1$ results in a rather good fit to the amplitude temperature dependence (see Fig. 2 (c)). The observed gap magnitude is close to the magnitude of the largest of the two SDW gaps obtained from the optical conductivity.[33] Since the inter-band scattering is strong, as argued below, the

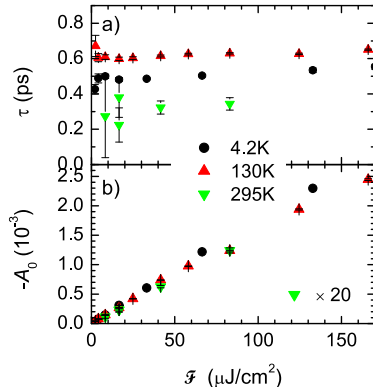


Figure 4: (Color online) Fluence dependence of the $\Delta R/R$ transient amplitude and relaxation time at different temperatures.

smallest of the gaps should present the bottleneck for the hot carrier energy relaxation so our data do not confirm the existence of the smaller gap suggested by Hu *et al.*[33].

Similarly to the case of SmFeAsO[23] we observe no decrease of the relaxation time with $\mathcal{F}$ as predicted by Kabanov *et al.*[5]. We also observe no divergence of the relaxation time with decreasing T such as in heavy fermion SDW UNiGa₅,[34] which, similar to as SrFe₂As₂,[35] remains metallic[36] upon the SDW gap opening. We can rule out the ballistic hot electron escape as a source of the low- T relaxation-time divergence cutoff,[37] due to the relatively high resistivity of SrFe₂As₂[35] and large optical penetration depth of ~ 60 nm at $\hbar\omega_{\text{probe}} = 1.55$ eV.[44] However, in iron pnictides, due to the presence of ungapped electronic bands below T_{SDW} , the energy relaxation is not limited by the anharmonic energy transfer from the high frequency to the low frequency phonons, but rather by the inter-band scattering (IBS) from the states at the edge of the SDW gap to the states in ungapped band(s) with energies $\epsilon - \epsilon_F \gg k_B T$ (see inset to Fig. 3(b)). Such scattering can be enhanced by the presence of impurities, which may explain the difference between the higher residual resistivity SrFe₂As₂ and lower residual resistivity UNiGa₅.

The absence of multiple relaxation components (apart from diffusion) from the $\Delta R/R$ transients together with IBS imply that mainly the hot carriers from the SDW gaped electronic bands contribute to the photoinduced reflectivity transients. This does not hinder the determination of $\lambda\langle(\hbar\omega)^2\rangle$ at high temperatures, since the IBS is essentially a momentum scattering, which becomes faster than the energy relaxation rate at high temperatures.

By means of the femtosecond optical pump-probe spectroscopy we determined the second moment of the Eliash-

berg function in SDW SrFe₂As₂ and compared it to SmFeAsO and BaFe₂As₂. In all compounds the values are similar (see Table I) suggesting moderate values of the electron phonon coupling constant λ as suggested by the linear response theory,[30] unless $\alpha^2 F(\omega)$ is strongly enhanced in the low-energy phonons region.

Below T_{SDW} the temperature dependence of the relaxation indicates the appearance of a quasi-particle relaxation bottleneck due to opening of a single charge gap at T_{SDW} with a BCS-like temperature dependence similar to that observed[23] in SmFeAsO and inferred from the recently published data[38] in BaFe₂As₂.

	$\lambda\langle(\hbar\omega)^2\rangle$ (meV ²)	$\lambda\langle(\hbar\omega)^2\rangle/\lambda$ (meV ²)	λ	$2\Delta_{\text{SDW}}/k_B T_{\text{SDW}}$
SrFe ₂ As ₂	110 ± 10	430	~ 0.25	7.2 ± 1
SmFeAsO ref.[23]	135 ± 10	770	~ 0.18	~ 5
BaFe ₂ As ₂ ^a	$\sim 65^b$	430	~ 0.15	4.7 ± 1.6

^aWe used the data from the supplemental material of Chia *et al.* [38]. (<http://prl.aps.org/supplemental/PRL/v104/i2/e027003>).

^bOnly data just above $T_{\text{SDW}} \simeq 130\text{K}$ is available so the value might be underestimated.

Table I: Electron phonon coupling parameters and SDW gap magnitudes in SDW iron-pnictides. The experimental inelastic-neutron-scattering phonon spectra from Mittal *et al.* [29, 39] and Osborn *et al.* [40] were used to estimate $\lambda\langle(\hbar\omega)^2\rangle/\lambda$ assuming $\alpha^2 F(\omega)$ has the phonon DOS shape.

This work has been supported by Slovenian Research Agency and the National Science Foundation of China .

-
- [1] Y. Kamihara, H. Hiramatsu, M. Hirano, R. Kawamura, H. Yanagi, T. Kamiya, and H. Hosono, *Journal of the American Chemical Society* **128**, 10012 (2006), URL <http://dx.doi.org/10.1021/ja063355c>.
 - [2] Y. Kamihara, T. Watanabe, M. Hirano, H. Hosono, et al., *J. Am. Chem. Soc.* **130**, 3296 (2008).
 - [3] Z. Ren, G. Che, X. Dong, J. Yang, W. Lu, W. Yi, X. Shen, Z. Li, L. Sun, F. Zhou, et al., *EPL-Europhysics Letters* **83**, 17002 (2008).
 - [4] C. J. Stevens, D. Smith, C. Chen, J. F. Ryan, B. Podobnik, D. Mihailovic, G. A. Wagner, and J. E. Evetts, *Phys. Rev. Lett.* **78**, 2212 (1997).
 - [5] V. V. Kabanov, J. Demsar, B. Podobnik, and D. Mihailovic, *Phys. Rev. B* **59**, 1497 (1999).
 - [6] J. Demsar, B. Podobnik, V. V. Kabanov, T. Wolf, and D. Mihailovic, *Phys. Rev. Lett.* **82**, 4918 (1999).
 - [7] R. Kaindl, M. Woerner, T. Elsaesser, D. Smith, J. Ryan, G. Farnan, M. McCurry, and D. Walmsley, *Science* **287**, 470 (2000).
 - [8] D. Dvorsek, V. V. Kabanov, J. Demsar, S. M. Kazakov, J. Karpinski, and D. Mihailovic, *Phys. Rev. B* **66**, 020510 (2002).
 - [9] G. P. Segre, N. Gedik, J. Orenstein, D. A. Bonn, R. Liang, and W. N. Hardy, *Phys. Rev. Lett.* **88**, 137001 (2002).

- [10] M. Schneider, J. Demsar, Y. Glinka, A. Klimov, A. Krapf, S. Rast, Y. Ren, et al., *EPL (Europhysics Letters)* **60**, 460 (2002).
- [11] J. Demsar, R. D. Averitt, A. J. Taylor, V. V. Kabanov, W. N. Kang, H. J. Kim, E. M. Choi, and S. I. Lee, *Phys. Rev. Lett.* **91**, 267002 (2003).
- [12] N. Gedik, J. Orenstein, R. Liang, D. Bonn, and W. Hardy, *Science* **300**, 1410 (2003).
- [13] N. Gedik, P. Blake, R. C. Spitzer, J. Orenstein, R. Liang, D. A. Bonn, and W. N. Hardy, *Phys. Rev. B* **70**, 014504 (2004).
- [14] P. Kusar, J. Demsar, D. Mihailovic, and S. Sugai, *Phys. Rev. B* **72**, 014544 (2005).
- [15] R. A. Kaindl, M. A. Carnahan, D. S. Chemla, S. Oh, and J. N. Eckstein, *Phys. Rev. B* **72**, 060510 (2005).
- [16] V. V. Kabanov, J. Demsar, and D. Mihailovic, *Phys. Rev. Lett.* **95**, 147002 (2005).
- [17] G. Bianchi, C. Chen, M. Nohara, H. Takagi, and J. F. Ryan, *Phys. Rev. B* **72**, 094516 (2005).
- [18] M. L. Schneider, M. Onellion, X. X. Xi, X. Zeng, A. Soukiassian, P. Omernik, and G. Taft, *Phys. Rev. B* **70**, 012504 (2004).
- [19] T. Mertelj, V. Kabanov, C. Gadermaier, N. Zhigadlo, S. Katrych, J. Karpinski, and D. Mihailovic, *Physical Review Letters* **102**, 117002 (2009).
- [20] T. Mertelj, V. Kabanov, C. Gadermaier, N. Zhigadlo, S. Katrych, Z. Bukowski, J. Karpinski, and D. Mihailovic, *Journal of Superconductivity and Novel Magnetism* **22**, 575 (2009).
- [21] E. E. M. Chia, D. Talbayev, J.-X. Zhu, H. Q. Yuan, T. Park, J. D. Thompson, C. Panagopoulos, G. F. Chen, J. L. Luo, N. L. Wang, et al., *Phys. Rev. Lett.* **104**, 027003 (2010).
- [22] D. H. Torchinsky, G. F. Chen, J. L. Luo, N. L. Wang, and N. Gedik, *ArXiv e-prints* (2009), 0905.0678.
- [23] T. Mertelj, P. Kusar, V. V. Kabanov, L. Stojchevska, N. D. Zhigadlo, S. Katrych, Z. Bukowski, S. Weyeneth, J. Karpinski, and D. Mihailovic, *arXiv: 1001.1047* (2010).
- [24] V. V. Kabanov and A. S. Alexandrov, *Physical Review B (Condensed Matter and Materials Physics)* **78**, 174514 (pages 8) (2008), URL <http://link.aps.org/abstract/PRB/v78/e174514>.
- [25] P. Kusar, V. Kabanov, J. Demsar, T. Mertelj, S. Sugai, and D. Mihailovic, *Physical Review Letters* **101**, 227001 (2008).
- [26] L. Li, Y. Luo, Q. Wang, H. Chen, Z. Ren, Q. Tao, Y. Li, X. Lin, M. He, Z. Zhu, et al., *New Journal of Physics* **11**, 025008 (2009).
- [27] T. Mertelj, A. Ošlak, J. Dolinšek, I. Fisher, V. Kabanov, and D. Mihailovic, *Physical Review Letters* **102**, 86405 (2009).
- [28] C. Gadermaier, A. S. Alexandrov, V. V. Kabanov, P. Kusar, T. Mertelj, X. Yao, C. Manzoni, G. Cerullo, and D. Mihailovic, *ArXiv e-prints* (2009), 0902.1636.
- [29] R. Mittal, M. Zbiri, S. Rols, Y. Su, Y. Xiao, H. Schober, S. L. Chaplot, M. Johnson, T. Chatterji, Y. Inoue, et al., *arXiv: 0912.1782* (2009).
- [30] L. Boeri, O. V. Dolgov, and A. A. Golubov, *Phys. Rev. Lett.* **101**, 026403 (2008).
- [31] S. Sebastian, J. Gillett, N. Harrison, P. Lau, D. Singh, C. Mielke, and G. Lonzarich, *Journal of Physics: Condensed Matter* **20**, 422203 (2008).
- [32] J. Analytis, R. McDonald, J. Chu, S. Riggs, A. Bangura, C. Kucharczyk, M. Johannes, and I. Fisher, *Physical Review B* **80**, 64507 (2009).
- [33] W. Hu, J. Dong, G. Li, Z. Li, P. Zheng, G. Chen, J. Luo, and N. Wang, *Phys Rev Lett* **101**, 257005 (2008).
- [34] E. E. M. Chia, J.-X. Zhu, H. J. Lee, N. Hur, N. O. Moreno, E. D. Bauer, T. Durakiewicz, R. D. Averitt, J. L. Sarrao, and A. J. Taylor, *Phys. Rev. B* **74**, 140409 (2006).
- [35] G. F. Chen, Z. Li, J. Dong, G. Li, W. Z. Hu, X. D. Zhang, X. H. Song, P. Zheng, N. L. Wang, and J. L. Luo, *Phys. Rev. B* **78**, 224512 (2008).
- [36] N. O. Moreno, E. D. Bauer, J. L. Sarrao, M. F. Hundley, J. D. Thompson, and Z. Fisk, *Phys. Rev. B* **72**, 035119 (2005).
- [37] J. Demsar, V. V. Kabanov, A. S. Alexandrov, H. J. Lee, E. D. Bauer, J. L. Sarrao, and A. J. Taylor, *Phys. Rev. B* **80**, 085121 (2009).
- [38] E. E. M. Chia, D. Talbayev, J.-X. Zhu, H. Q. Yuan, T. Park, J. D. Thompson, C. Panagopoulos, G. F. Chen, J. L. Luo, N. L. Wang, et al., *Phys. Rev. Lett.* **104**, 027003 (2010).
- [39] R. Mittal, Y. Su, S. Rols, T. Chatterji, S. L. Chaplot, H. Schober, M. Rotter, D. Johrendt, and T. Brueckel, *Phys. Rev. B* **78**, 104514 (2008).
- [40] R. Osborn, S. Rosenkranz, E. Goremychkin, and A. Christianson, *Physica C: Superconductivity and its applications* **469**, 498 (2009).
- [41] K. Ishida, Y. Nakai, H. Hosono, Y. Kuramoto, H. Kusunose, A. Kiss, R. Kubo, M. Fujita, K. Wakabayashi, K. Nakada, et al., *J. Phys. Soc. Jpn* **78**, 062001 (2009).
- [42] A. V. Boris, N. N. Kovaleva, S. S. A. Seo, J. S. Kim, P. Popovich, Y. Matiks, R. K. Kremer, and B. Keimer, *Physical Review Letters* **102**, 027001 (pages 4) (2009), URL <http://link.aps.org/abstract/PRL/v102/e027001>.
- [43] For a recent review see ref. 41.
- [44] The optical penetration depth estimation is based on the ellipsometry data in LaFeAsO[42] and similarity of the optical conductivity in SrFe₂As₂[33] to that of LaFeAsO.